

The infrared spectrum of $\text{Na}_{0.57}\text{CoO}_2$

S. Lupi, M. Ortolani, and P. Calvani

Coherentia-INFM and Dipartimento di Fisica, Università di Roma La Sapienza, Piazzale Aldo Moro 2, I-00185 Roma, Italy

(Dated: February 2, 2008)

The optical conductivity of single crystals of Na_xCoO_2 (for $x = 0.57$) is first reported between 295 and 30 K. In the far infrared, an "anomalous Drude" analysis leads to a carrier effective mass of 5 ± 1 electron masses. That this high value is due to strong electron-phonon coupling is suggested by the Fano distortion of a phonon at 570 cm^{-1} . A peak at 8800 cm^{-1} scales with the charge transfer band of several high- T_c cuprates by simply replacing the in-plane Cu-O bond length with that for Co-O.

PACS numbers: 78.30.-j, 74.25.Gz, 74.25.Kc

The layered oxides Na_xCoO_2 have attracted the attention of the scientific community after the discovery that samples with $x \simeq 0.3$ become superconducting, below $T_c \simeq 5 \text{ K}$, after exposure to humid air.[1] These hole-doped metals have a hexagonal structure, with the ab planes formed by CoO_2 sheets intercalated by layers of Na^+ ions. Water molecules between those planes increase the lattice parameter along the c -axis from 1.09 to 1.96 nm.[1] However, how water inclusion triggers superconductivity in Na_xCoO_2 is not fully understood yet. Therefore, also the investigation of non-hydrated samples is deserving a considerable research effort. Na_xCoO_2 is considered to be a strongly correlated system, with a Hubbard splitting $U \sim 5 \text{ eV}$. The conduction band should be narrow, with an effective mass of the carriers $m^* \sim 7m$,[6] where m is the bare electron mass. In the ab planes, the resistivity $\rho(T)$ is quasi-linear with T for $x = 0.7$,[2] with a change of slope around 100 K, while for $x = 0.75$ $\rho(T)$ is suggestive of a spin ordering instability below 22 K.[3] For $x = 0.57$, $\rho(T)$ follows a $T^{3/2}$ law in the ab plane[4] below 175 K. Along the c axis, it has a maximum at the same temperature.[5] The latter behavior may be related with the growth, at low temperature, of a coherent quasi-particle peak in the density of states measured by Angle Resolved Photoemission Spectroscopy (ARPES).[5]

In the optical domain, only room-temperature Raman data are presently available to our knowledge: those of Iliev *et al.*[7] on $\text{Na}_{0.7}\text{CoO}_2$ and those of Lemmens *et al.* on $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$. [8] Group theory predicts $4E_{1g} + 4A_{1g}$ Raman active modes. However, the spectra of dry powders show one E_{1g} phonon at 480 cm^{-1} and one A_{1g} mode at 598 cm^{-1} . In the ab planes of single crystals with $x \simeq 0.7$, one observes a mode at 588 cm^{-1} with weak satellites and, in the hydrated compound, an additional peak at 470 cm^{-1} . All these values may change considerably after sample ageing and/or surface treatment. To our knowledge, no infrared data are presently available for the system Na_xCoO_2 . However, they might provide valuable information on the charge dynamics, complementary to that collected by ARPES and transport measurements. The present paper is aimed at filling this gap.

Our experiment was made possible by the use of mosaics of $\text{Na}_{0.57}\text{CoO}_2$ single crystals. They were protected from humidity by keeping them in dry air at $+45^\circ\text{C}$, and

in a high vacuum when mounted in the cryostat. All of them were grown from the flux as described in Ref. 4 and were extracted from the same batch. After growth, x resulted to be 0.57, the closest value to 0.5 that could be obtained.[4] Ten to twelve small crystals were mounted on the sample holder. The resulting mosaic surface was approximately $2 \times 2 \text{ mm}$ wide. The crystal surfaces, that are excellent ab planes as they are flux-grown, were coplanar within a few degrees. This was obtained by monitoring the reflections of a laser beam focused on the individual crystals and adjusting their positions while the glue (silver paint) was drying. The eventual contribution of the c axis due to residual disalignment of a crystal was largely reduced by the effect of refraction, which bends the radiation wavevector toward the normal to the surface. As final check, the reflectivity of one crystal was measured at room temperature by an infrared microscope Hyperion 2000, mounted onto a Bruker IFS 66V interferometer, between 400 and $17,000 \text{ cm}^{-1}$. The reference was the crystal itself after exposure to gold evaporation. The resulting $R(\omega)$ (solid line) is compared with that of the mosaic at the same temperature (dotted line) in the inset of Fig. 1.

The $R(\omega)$ of the mosaic was measured between 30 and 295 K, and between 40 and 10000 cm^{-1} at quasi-normal incidence (8°), by a Bomem DA3 interferometer. The final alignment of the reflectivity setup was performed by remotely controlled motors, in order to compensate for the mechanical stress of the interferometer optics after the evacuation. The reference was a gold film evaporated *in situ* onto the sample by displacing a hot filament in front of it. The $R(\omega)$ thus measured is shown at different temperatures in Fig. 1. The complex optical conductivity $\tilde{\sigma}(\omega)$ was then obtained by standard Kramers-Kronig relations. A Hagen-Rubens extrapolation was employed below 40 cm^{-1} , an extrapolation based on fits by Lorentzians and polynomials was used above $17,000 \text{ cm}^{-1}$. An alternative extrapolation based on the reflectivity[9] of NdCoO_3 gave the same results within errors. As the surface of the flux-grown crystals is intrinsically ab , the $\tilde{\sigma}(\omega)$ obtained in this way is the optical conductivity of the CoO_2 sheets of $\text{Na}_{0.57}\text{CoO}_2$.

The real part of $\tilde{\sigma}(\omega)$, $\sigma_1(\omega)$, is shown at two temperatures in Fig. 2. In both sets of data, the main features

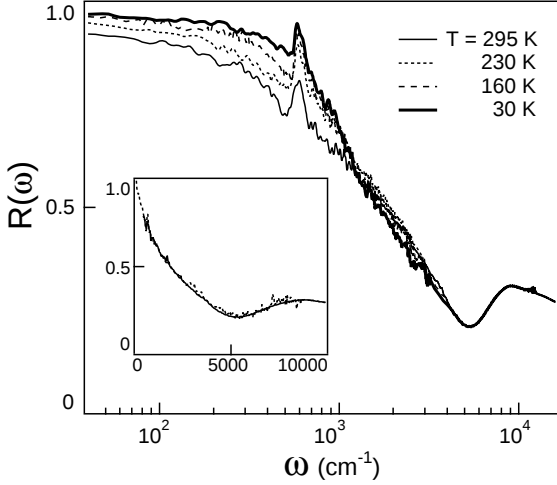


FIG. 1: The reflectivity of a mosaic of coplanar $\text{Na}_{0.57}\text{CoO}_2$ crystals at different temperatures, measured with the electric field in the ab plane. In the inset, the $R(\omega)$ of the mosaic at 295 K (dotted line) is compared with that measured on a single crystal by an infrared microscope (solid line).

are a metallic conductivity in the far and mid infrared, a phonon line, and a broad absorption in the near infrared. This latter exhibits an edge around 6000 cm^{-1} and a well defined peak at $\Delta = 8800 \text{ cm}^{-1}$. This energy roughly corresponds to that (0.7 eV) of a peak observed in ARPES spectra, and assigned to Co t_{2g} -derived states.[2, 6] However, the infrared band at 8800 cm^{-1} can be rather attributed to charge transfer (CT) between the Co $3d$ orbitals and the O $2p$ orbitals. This assignment is supported by scaling the energy of the band of $\text{Na}_{0.57}\text{CoO}_2$ with that of the corresponding bands of the cuprates. In high- T_c materials, where the Cu-O bonds of length d are hybridized $p-d$ and have a octahedral coordination, the CT peak energy Δ is found to follow a law $\Delta \propto d^{-7}$. [10, 11] The same hybridization and coordination are present in Na_xCoO_2 , despite its unit cell being hexagonal instead of tetragonal. As shown in the inset of Fig. 2, the present value of Δ for the CoO_2 sheets (where $d_{\text{Co-O}} = 0.210 \text{ nm}$) is in excellent agreement with the prediction obtained by extrapolating the d^{-7} law which holds for cuprates. The latter compounds in Fig. 2 are undoped, unlike $\text{Na}_{0.57}\text{CoO}_2$. However, it has been shown that the energy of the charge-transfer band in $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ is approximately independent of doping.[12]

The conductivity of oxides within the charge-transfer gap has been often described in terms of an "anomalous-Drude" model, where both the effective mass $m^*(\omega)$ and the relaxation rate $\tau^{-1}(\omega)$ of the carriers are allowed to depend on frequency. Both those quantities, as well as the plasma frequency ω_p , can be directly extracted[13] from $\tilde{\sigma}(\omega)$. The results for $\text{Na}_{0.57}\text{CoO}_2$ are shown in Fig. 3. The strong phonon absorption around 570 cm^{-1} , that will be discussed later on, does not prevent one from ob-

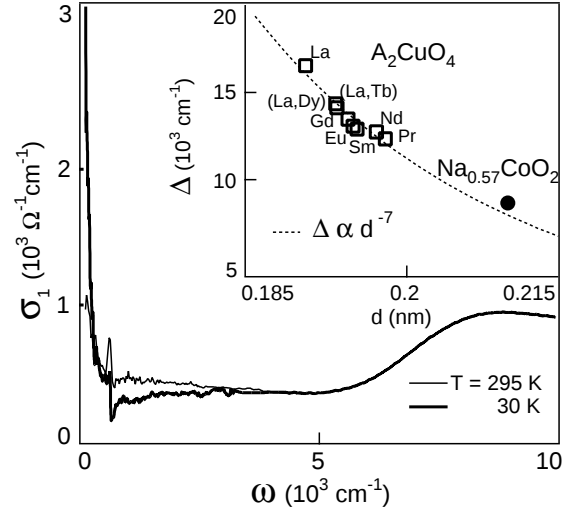


FIG. 2: $\sigma(\omega)$ at different temperatures, as extracted from the reflectivity of Fig. 1. In the inset, the energy Δ of the peak here observed in the near infrared (full circle) is compared with those reported in Ref. 10 for the charge-transfer bands of several cuprates belonging to the family A_2CuO_4 , with A = La, (La,Tb), (La,Dy), Gd, Nd, Eu, Sm, Pr (squares). The dashed line is a $\Delta \propto d^{-7}$ law, where d is the ab plane Co-O, or Cu-O distance, respectively.

taining information on the carrier parameters. First, for $\omega \lesssim 1500 \text{ cm}^{-1}$, an "anomalous Drude" regime indeed holds, where both m^*/m and τ^{-1} depend on ω . There is no indication for the opening of a pseudogap[13] down to 30 K, which would suggest either charge localization or pair pre-formation. Secondly, at any T , $m^*(\omega)/m \rightarrow 5 \pm 1$ for $\omega \rightarrow 0$, in satisfactory agreement with the photoemission data cited above.[6] Thirdly, below a temperature T_0 between 230 and 160 K, $\tau^{-1} \propto \omega^{3/2}$ (see the inset of Fig. 3). Moreover, below T_0 its low-frequency values become independent of T within errors. This is clearly suggestive of a change in the transport properties and may be related to the crossover observed at $T_M \sim 180 \text{ K}$ both in the ARPES spectra[5] of $\text{Na}_{0.57}\text{CoO}_2$ and in its resistivity,[4, 5] which is proportional to $T^{3/2}$ below T_M .

The E_{1u} optical phonon observed around 570 cm^{-1} deserves a detailed description. Four of such modes are predicted by group analysis but, as for Raman spectra cited above,[7] just one line is observed here. It can be assigned to the Co-O stretching,[14] consistently with its strong hardening for decreasing temperature (see $\tilde{\omega}_F$ in Table I). In the present infrared spectra, the other phonon lines, which are expected to occur at lower frequencies than the Co-O stretching, are probably shielded by the narrow free-carrier continuum in a more efficient way.

The phonon line around 570 cm^{-1} , as shown in the inset of Fig. 4, exhibits a pronounced Fano distortion. This indicates a strong coupling between the Co-O stretching and the Drude-like continuum, which indeed has most of

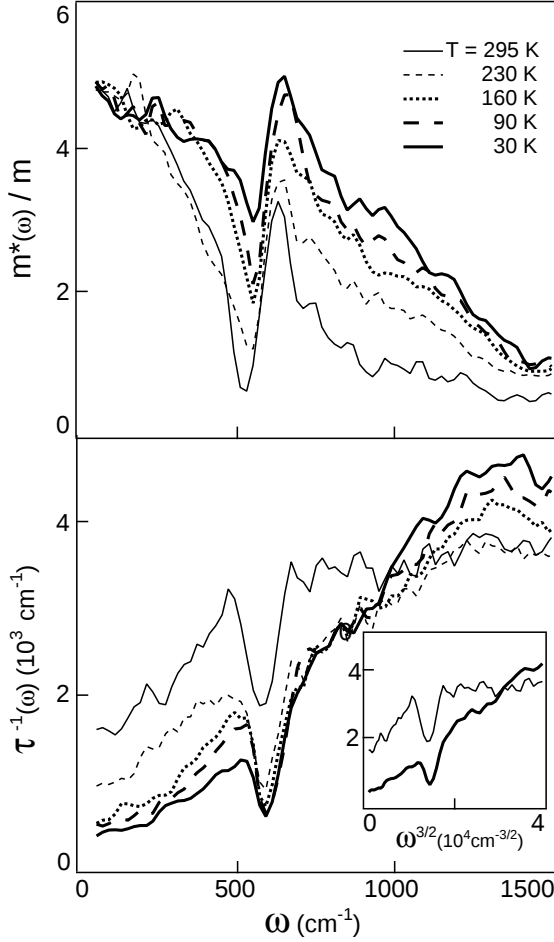


FIG. 3: Effective mass (top) and relaxation rate (bottom) vs. frequency, as obtained from $\tilde{\sigma}(\omega)$ of $\text{Na}_{0.57}\text{CoO}_2$. In the inset, $\tau^{-1}(\omega)$ is plotted vs. $\omega^{3/2}$ both at room temperature (thin line) and at 30 K (thick line).

its spectral weight on the opposite side of the absorption minimum.[15] The effect is more and more evident as T is lowered. The observed spectrum can be accurately fitted at all temperatures by the Fano equation for the dielectric function[15, 16]

$$\epsilon_{2F}(\omega) = R \left(\frac{(q\gamma_F + (\omega - \tilde{\omega}_F))^2}{\gamma_F^2 + (\omega - \tilde{\omega}_F)^2} - 1 \right). \quad (1)$$

Therein, $\tilde{\omega}_F$ is the renormalized frequency of the phonon and γ is its half width, which here basically measures the electron-phonon interaction strength. R is a scale parameter which includes the transition rates, and q is the Fano-Breit-Wigner parameter, which measures the reciprocal of the electron-phonon interaction once weighted for the density of states of the continuum.[17]

The quantities in Eq. 1, as provided by the fit to data, are reported in Table I. One may notice that γ_F , which measures the electron-phonon interaction, is large and independent of temperature within the errors reported in

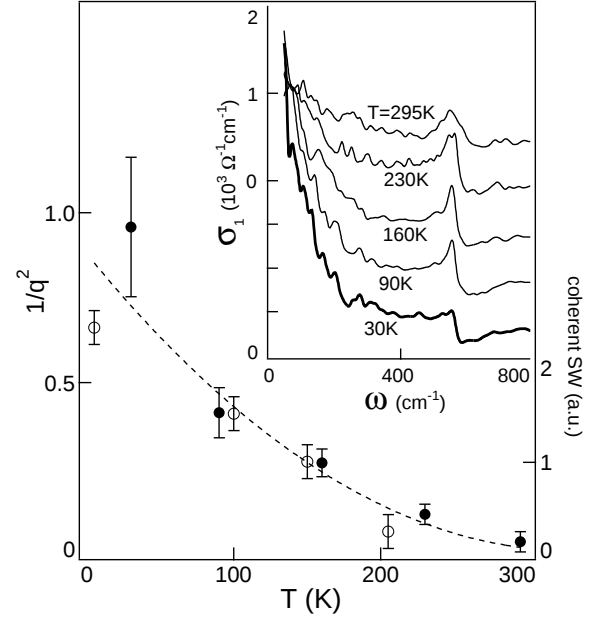


FIG. 4: The Fano parameter $1/q^2$ of the phonon at 570 cm^{-1} (dots) is reported vs. T and compared with the spectral weight SW of the coherent ARPES peak in Ref. 5 (circles). The SW at 150 K has been normalized to the $1/q^2$ value at 160 K. The dashed line is a guide to the eye. In the inset, the observed Fano profile is shown at different temperatures. An offset has been introduced for sake of clarity.

TABLE I: Values of the Fano parameters in Eq. 1, as provided by the fit to data at five temperatures. An estimate of the average experimental uncertainty, which holds for all temperatures, is given in parenthesis.

T (K)	295	230	160	90	30
q	-5.7(0.2)	-3.1	-1.9	-1.6	-1.0
R	1.0(0.3)	6.9	14.6	18.2	21.3
γ_F (cm^{-1})	21(5)	25	18	19	26
$\tilde{\omega}_F$ (cm^{-1})	562(2)	563	566	569	575

parenthesis. On the other hand, as already mentioned, $\tilde{\omega}_F$ appreciably increases as $T \rightarrow 0$. Also $1/q^2$ steadily increases for decreasing T as shown in Fig. 4. Therein, its behavior is shown to be consistent with that of the spectral weight of the coherent peak which appears in the ARPES spectra, close to the Fermi level, for $T < 200$ K. Indeed, as the electron-phonon interaction γ_F is T -independent in Table I, and the same holds for the matrix element of the dipolar Hamiltonian, the T -dependence of $1/q^2$ probes that of the density of states of the continuum at the phonon energy.

In conclusion, we have reported here the reflectivity spectra of single crystals of $\text{Na}_{0.57}\text{CoO}_2$ in the ab plane. The resulting optical conductivity exhibits a near infrared peak that can be attributed to $\text{Co}(3d)\text{-O}(2p)$

charge transfer. Indeed, it scales with that charge transfer band observed in the cuprates by simply replacing the Cu-O in-plane bond length with the Co-O bond length. In the far infrared, $\tilde{\sigma}(\omega)$ can be described by an anomalous Drude behavior, where the carriers have an effective mass of about $5m$. Their relaxation rate varies as $\omega^{3/2}$ and is independent of T , within errors, below a temperature T_0 . T_0 is consistent with the crossover temperature T_M below which either $\rho(T) \propto T^{3/2}$ and a quasiparticle peak appears in the photoemission spectra of $\text{Na}_{0.57}\text{CoO}_2$.

Only one unshielded phonon has been observed in the present spectra, namely the transverse optical Co-O stretching mode. It exhibits a marked Fano profile, which is suggestive of a strong electron-phonon coupling. This is consistent with the high effective mass of the car-

riers, which therefore could be polaronic in nature. Under this assumption, the observation of the quasiparticle photoemission peak below T_M and, here, of a τ^{-1} independent of T below T_0 , may be interpreted in terms of coherent (tunneling) propagation of large polarons. On the other hand, even if we observe a broad background in the midinfrared, which cannot be described in terms of Drude-like models, we cannot identify any clear polaronic "shake-off" band in the present data. Systematic infrared investigations of the Na_xCoO_2 system as a function of doping and temperature would be needed to clearly identify the nature of the carriers.

We wish to thank F. Rivadulla for producing and characterizing the samples here measured, as well as for many valuable discussions.

-
- [1] K. Takada *et al.*, Nature **422**, 53 (2003).
 - [2] M. Z. Hasan *et al.*, cond-mat/0308438 (2003).
 - [3] T. Motohashi *et al.*, Phys. Rev. B **67**, 064406 (2003).
 - [4] F. Rivadulla *et al.*, Phys. Rev. B **68**, 075108 (2003).
 - [5] T. Valla *et al.*, Nature **417**, 627 (2002).
 - [6] H-B. Yang *et al.*, cond-mat/0310532 (2003).
 - [7] M. N. Iliev *et al.*, unpublished.
 - [8] P. Lemmens *et al.*, cond-mat/0309186 (2003).
 - [9] I. Terasaki *et al.*, Phys. Rev. B **43**, 551 (1991).
 - [10] Y. Tokura *et al.*, Phys. Rev. B **45**, 7580 (1992).
 - [11] S. L. Cooper *et al.*, Phys. Rev. B **42**, 10785 (1990).
 - [12] A. Lucarelli *et al.*, Phys. Rev. Lett. **90**, 037002 (2003).
 - [13] A. V. Puchkov *et al.*, J. Phys.: Condensed Matter **8**, 10049 (1996).
 - [14] L. Sudheendra *et al.*, Chem. Phys. Lett. **340**, 275 (2001).
 - [15] S. Lupi *et al.*, Phys. Rev. B **57**, 1248 (1998).
 - [16] L. C. Davis and L. A. Feldkamp, Phys. Rev. B **15**, 2961 (1977).
 - [17] U. Fano, Phys. Rev. **124**, 1866 (1961).